

Reentrant spin glass transition in $\text{La}_{0.96-y}\text{Nd}_y\text{K}_{0.04}\text{MnO}_3$: origin and effects on the colossal magnetoresistivity

R. MATHIEU¹, P. SVEDLINDH¹, and P. NORDBLAD¹

¹ *Department of Materials Science, Uppsala University, Box 534, SE-751 21 Uppsala, Sweden*

PACS. 75.30.Vn – Colossal magnetoresistance.

PACS. 75.50.Lk – Spin glasses and other random magnets.

Abstract. – Magnetic, electric and structural properties of $\text{La}_{0.96-y}\text{Nd}_y\text{K}_{0.04}\text{MnO}_{3+\delta}$ with $0 \leq y \leq 0.4$ have been studied experimentally. A disordered magnetic state is formed as La is substituted by Nd, reflecting the competition between ferromagnetic (FM) double exchange and antiferromagnetic superexchange interactions. Key structural parameters are identified and correlated with changes in magnetic and electric properties. By application of a large magnetic field, spin disorder scattering is removed, creating a new magnetoresistance peak at a temperature lower than the first near- T_c peak. Time dependent zero-field-cooled magnetisation measurements have been performed for $y=0.4$ around this temperature. A reentrant spin glass (RSG) transition is evidenced, with low field ageing properties in both the RSG and FM phases, similar to those observed in archetypal spin glass materials.

Introduction. – The doped manganite compounds $\text{R}_{1-y}\text{A}_y\text{MnO}_3$ (R=rare earth; A=alkaline earth) have been intensively investigated concerning their colossal magnetoresistance (CMR) properties [1]. Simultaneous ferromagnetic (FM) and metallic properties in these manganese oxides are attributed to double exchange [2] (DE) interaction between pairs of Mn^{3+} ($t_{2g}^3 e_g^1$) and Mn^{4+} (t_{2g}^3) ions. Substitution of cations with different sizes at the rare earth sites results in lattice distortions that may influence the ferromagnetic DE and the antiferromagnetic (AFM) superexchange interactions differently, for instance increasing the importance of the AFM interactions with respect to the FM interactions. This can create various forms of magnetic disorder, thereby also affecting the transfer integral for itinerant e_g electrons which depends on the relative spin orientation of the localized t_{2g} moments; $t_{ij} \propto \cos(\theta_{ij}/2)$, where θ_{ij} is the angle between moments i and j [3]. In systems with ferromagnetic DE interaction dominating, the AFM interactions may still cause magnetic disorder and frustration and the system is in this case expected to show a low temperature reentrant spin glass (RSG) phase [4, 5]. When such a system is cooled from a high temperature, it first exhibits a transition from a paramagnetic (PM) to a ferromagnetic (FM) phase. If the cooling proceeds, a transition to a RSG phase occurs. Indications of such a transition have already been reported for CMR compounds, but without presenting convincing experimental evidences for its existence. Usually, the authors consider that a low temperature cusp in the zero-field-cooled

(ZFC) magnetisation, leading to a difference between the ZFC and field cooled (FC) magnetisation curves at low temperatures, is enough to evidence a low temperature RSG phase [6–9]. Ac-susceptibility measurements are sometimes added; a frequency dependent ac-susceptibility is then attributed to the RSG phase [10–12]. But, even if these features are indicative of a deviation from a perfectly ordered ferromagnetic state, they are not sufficient to prove a low temperature RSG phase. Moreover, it is possible to envisage other disordered magnetic phases resulting from a competition between ferromagnetic DE and antiferromagnetic superexchange interactions. Low temperature spin canted AF and FM phases were suggested in the pioneering work of de Gennes [3]. More recent work indicates that the canted phase is unstable against electronic phase separation and the formation of hole rich ferromagnetic and hole undoped antiferromagnetic regions [13,14]. Thus, other and complementary experiments must be performed to dissolve the details of the magnetic phase diagram of the manganese perovskites. For example in a disordered and frustrated magnetic system like a spin glass, the zero-field cooled (ZFC) magnetisation relaxes in a characteristic way if the temperature is kept constant; therefore time-dependent ZFC magnetisation measurements may be used to study the evolution of the spin configuration and the possible occurrence of a RSG phase. In the present study, we investigate effects of ion size mismatch induced by replacing La^{3+} with Nd^{3+} in the manganese oxide $\text{La}_{0.96-y}\text{Nd}_y\text{K}_{0.04}\text{MnO}_{3+\delta}$. A RSG phase transition, creating a second peak in the magnetoresistance when applying a sufficiently large magnetic field, is revealed from ZFC relaxation measurements. The results give evidence in support of a recent proposal that the AFM superexchange interaction is one mechanism responsible for spin disorder and that the DE ferromagnetic interaction is more strongly affected by a variation of the $Mn - O - Mn$ bond with cation substitution [15].

Samples and Experiments. – Single-phase $\text{La}_{0.96-y}\text{Nd}_y\text{K}_{0.04}\text{MnO}_{3+\delta}$, with y ranging from 0 to 0.4 in steps of 0.1 were prepared by solid state reaction between La_2O_3 , Nd_2O_3 , MnO_2 and K_2CO_3 in stoichiometric proportions. Substitution of Nd^{3+} at the La^{3+} site, Nd^{3+} having a smaller ionic radius, modifies the $Mn - O - Mn$ bond angle and the $Mn - O$ bond length. Structure and composition of the obtained compounds were checked by room temperature x-ray diffraction (XRD) on a high resolution STOE transmission diffractometer equipped with a position-sensitive detector. The scanning range was $10^\circ - 90^\circ$ and $\text{CuK}\alpha_1$ radiation was used for all data collections. We observe a change in structure from rhombohedral $R - 3C$ to orthorhombic $Pnma$; Table I gives a summary of the structural data; the change from $R - 3C$ to $Pnma$ at an average A-site ionic radius $\langle r_A \rangle = 1.225 \text{ \AA}$ is in full agreement with earlier reports [16]. For $y = 0.1$, with $\langle r_A \rangle = 1.224 \text{ \AA}$, it was necessary to include a mixture of the rhombohedral and the orthorhombic structures in the refinements.

Low field ac-susceptibility measurements, $\chi(f, T) = \chi'(f, T) + i\chi''(f, T)$, were performed in a LakeShore ac-susceptometer. Measurements of resistivity and magnetoresistance were performed using a Maglab 2000 system from Oxford Instruments; the magnetoresistance is defined as $(R_0 - R_H)/R_0$. Finally, time dependent ZFC magnetisation measurements were performed in a non-commercial SQUID magnetometer [17]. The sample was cooled in zero field from a temperature above T_c to the measurement temperature. After a waiting time (t_w), a weak magnetic field ($H=0.05$ to 1 Oe) was applied and the magnetisation $M(t)$ recorded vs. observation time t . The relaxation rate, defined as $S(t) = H^{-1} dM/d\log t$, was derived from these measurements.

Results and discussion. – The main frame of Fig. 1 shows $\chi'(f)$ and $\chi''(f)$ vs. temperature for the $y = 0$ and $y = 0.4$ samples. The Curie temperature (T_c), defined from the inflection point in $\chi'(f)$ decreases with increasing Nd doping. At the same time, a frequency

dependent knee is created in the in-phase component of the ac-susceptibility at a temperature $T_f(f) < T_c$, corresponding to a large and likewise frequency dependent peak in the out-of-phase component; $T_f(f)$ decreases with increasing Nd doping. This more pronounced frequency dependence of χ indicates that the magnetic state is more disordered at low temperatures. The magnetic disorder is a consequence of changes in the crystal structure induced by replacing La^{3+} with Nd^{3+} . The smaller $\text{Mn} - \text{O} - \text{Mn}$ bond angle (cf. Table I) will affect (decrease) not only the DE hopping integral between $e_g(\text{Mn})$ - $2p_\sigma(\text{O})$ - $e_g(\text{Mn})$ orbitals but also the AFM superexchange hopping integral between $t_{2g}(\text{Mn})$ - $2p_\pi(\text{O})$ - $t_{2g}(\text{Mn})$ orbitals. However, due to the nature of the $\text{dp}\pi$ hybridization, the AFM interaction is expected to be less influenced by changes in bond angle and will thus, relative to the FM DE interaction, increase in importance. The strong effect on the DE interaction is confirmed by the variation of the ferromagnetic transition temperature with bond angle presented in the insert of Fig. 1. In passing we note that disorder in the magnetic interactions may lead to one of several possible, distinctly different magnetic states; a spin canted state [3], a state with electronic phase separation between ferromagnetic and antiferromagnetic regions [13, 14], or a RSG state [4]. It is important to realize that these possible magnetic states are expected to display quite different magnetic and electrical behaviors, something which will be discussed more in detail below. Fig. 2 (a) presents the zero-field resistivity vs. temperature for all samples. A metal-insulator (M-I) transition occurs for Nd dopings $y = 0$ and $y = 0.1$ at a temperature close to T_c . As the Nd doping further increases the resistivity increases and no clear M-I transition is observed; the resistivity at low temperatures increases with decreasing temperature. By application of a large magnetic field, the spin disorder scattering induced by competing FM and AFM interactions is removed, creating a new magnetoresistance peak at a temperature lower than the first near- T_c peak (see Fig. 2 (b)); for $y=0.4$, this second peak is larger in magnitude than the first one. The second peak in the magnetoresistance appears at a temperature close to $T_f(f)$, suggesting a correlation between these different experimental observations. This is confirmed re-measuring χ'' with a superimposed dc field, as shown in Fig. 3. The dissipation is strongly suppressed by the dc field; at $H_{dc}=10^3$ Oe, the frequency dependent (cf. insert of Fig. 3) peaks in χ'' are still observed, shifted slightly to lower temperature, while at $H_{dc}=10^4$ Oe, the dissipation is very weak and the RSG like features are no longer observed. This indicates that, since the second peak in the magnetoresistance at T_f continues to develop increasing the field further (cf. Fig. 2 (b)), weak magnetic disorder remains, in the sense that the spin system is not fully collinear even after suppressing the slow spin dynamics of the RSG phase. The frequency dependence of the ac-susceptibility and the absence of a M-I transition for larger Nd dopings suggest that the ferromagnetic spin arrangement and the electronic configuration are perturbed. A transition from a FM metallic to an AFM partially charge ordered state with electronic phase separation of antiferro- and ferromagnetically ordered regions will result in a sharp decrease of χ' at the transition temperature as well as a likewise sharp increase of the resistivity [18]. Moreover, in partially charge ordered systems, application of a magnetic field drastically modifies the transport behavior; a relatively modest magnetic field will turn the insulating state to a metallic state [18, 19]. These characteristics are not observed in the presently investigated manganite system.

Another explanation for the observed spin-disorder is that a spin glass phase appears at low temperatures. One actually refers to a reentrant spin glass phase since the disordered magnetic phase appears at temperatures below where an ordered (ferromagnetic) phase first appears. This kind of samples have been extensively studied in the past, and it has been shown that RSG samples exhibit similar relaxation properties as conventional spin glasses [20]. In particular, the time dependence of the ZFC magnetisation depends on the time t_w used to equilibrate the spin system before applying a magnetic field. This dependence is revealed by an inflection

point in the $M(t)$ vs. $\log(t)$ curve, corresponding to a maximum in the relaxation rate $S(t)$ curve, at an observation time close to the waiting time $t \approx t_w$. The phenomenon is called ageing, and is an inherent property of disordered and frustrated spin systems, while this property is not expected to be part of the spin canted phase originally described by de Gennes [3]. Time dependent ZFC magnetisation measurements have been performed for the sample $y=0.4$ to study the behavior of the magnetic relaxation at temperatures both below and above the temperature where the disordered magnetic state appears. Fig. 4 (a) shows the relaxation rate $S(t)$ for $T = 50\text{K}$ (below $T_f(f)$) and $T = 110\text{K}$ (above $T_f(f)$), for different magnetic fields. The sample displays clear ageing behavior at both temperatures, with a waiting time dependence similar to that observed for ordinary spin glasses [20] as shown in the insert of Fig. 4, explicitly proving the RSG nature of the low temperature transition. The magnitude of the observed ageing phenomenon as well as the magnitude of the peak in $\chi''(T)$ prove the effect to be intrinsic to the material rather than confined to a possible spin disorder at grain boundaries. Also, as shown in Fig. 4 (b) the relaxation rate for $T = 50\text{K}$ indicates linear response of the magnetisation up to (relatively) high fields in the RSG phase. In the ferromagnetic phase (see Fig. 4 (b)), the response is non-linear even in weak magnetic fields and the ageing phenomenon is gradually suppressed when increasing the magnetic field, as it has also been observed in conventional reentrant spin glass materials [21].

Conclusion. – The resistivity of the $\text{La}_{0.96-y}\text{Nd}_y\text{K}_{0.04}\text{MnO}_{3+\delta}$ system increases with increasing y while the Curie temperature decreases, both observations indicating a lesser degree of FM double exchange interaction in favor of AFM superexchange interaction. The competition between FM and AFM exchange interactions results in spin disorder and frequency dependent characteristics of the ac-susceptibility; a frequency dependent peak in $\chi''(f, T)$ is observed at a temperature $T_f(f) < T_c$. The spin disorder is also evidenced by a second magnetoresistance peak at a temperature close to $T_f(f)$. Time dependent ZFC magnetisation measurements show ageing phenomena, both below and above $T_f(f)$, revealing the identity of the low temperature disordered magnetic state to be a reentrant spin glass phase. These results show the significance of the AFM superexchange interaction between localized $t_{2g}(\text{Mn})$ moments and how by substitution of cations it is possible to control its magnitude relative to the magnitude of the ferromagnetic DE interaction.

* * *

Financial support from the Swedish Natural Science Research Council (NFR) is acknowledged. The authors are grateful to Y. Guo for sample preparation and to Prof. Y. Anderson for help with structural analysis.

REFERENCES

- [1] A. P. RAMIREZ, *J. Phys.: Condens. Matter*, **9** (1997) 8171
- [2] C. ZENER, *Phys. Rev.*, **82** (1951) 403
- [3] P.-G. DE GENNES, *Phys. Rev.*, **118** (1960) 141
- [4] K. JONASON, J. MATTSSON, P. NORDBLAD, *Phys. Rev. B*, **53** (1996) 6507
- [5] K. JONASON, J. MATTSSON, P. NORDBLAD, *Phys. Rev. Lett.*, **77** (1996) 2562
- [6] T. TERA, T. KAKESHITA, T. FUKUDA, T. SABURI, N. TAKAMOTO, K. KINDO, M. HONDA, *Phys. Rev. B*, **58** (1998) 14908
- [7] X. J. FAN, J. H. ZHANG, X. G. LI, W. B. WU, J. Y. WAN, T. J. LEE, and H. C. KU, *J. Phys.: Condens. Matter*, **11** (1999) 3141-3148
- [8] J. ZHANG, F. WANG, P. ZHANG, and Q. YAN, *Jour. of Appl. Phys.*, **86** (1999) 1604

- [9] J. B. SHI, F. C. WU, C. T. LIN, *Appl. Phys. A*, **68** (1999) 577-581
- [10] J-W. CAI, C. WANG, B-G. SHEN, J-G. ZHAO, and W-S. ZHAN, *Appl. Phys. Lett.*, **71** (1997) 12
- [11] A. SUNDARESAN, A. MAIGNAN, and B. RAVEAU, *Phys. Rev. B*, **56** (1997) 5092
- [12] J. C. NIE, J. H. WANG, B. R. ZHAO, *J. Magn. Magn. Mater.*, **192** (1999) L379-L385
- [13] J. RIERA, K. HALLBERG, and E. DAGOTTO, *Phys. Rev. Lett.*, **79** (1997) 713
- [14] S. YUNOKI, J. HU, A. L. MALVEZZI, A. MOREO, N. FURUKAWA, and E. DAGOTTO, *Phys. Rev. Lett.*, **80** (1998) 845
- [15] HONGSUK YI, JAEJUN YU, and SUNG-IK LEE, *Phys. Rev. B*, **61** (2000) 428
- [16] P. G. RADAELLI, G. IANNONE, M. MAREZIO, H. Y. HWANG, S-W. CHEONG, J. D. JORGENSEN and D. N. ARGYRIOU, *Phys. Rev. B*, **56** (1997) 8265
- [17] J. MAGNUSSON, C. DJURBERG, P. GRANBERG, and P. NORDBLAD, *Rev. Sci. Instrum.*, **68** (1997) 3761
- [18] Y. TOMIOKA, A. ASAMITSU, Y. MORITOMO, H. KUWAHARA, and Y. TOKURA, *Phys. Rev. Lett.*, **74** (1995) 5108
- [19] Y. TOMIOKA, A. ASAMITSU, H. KUWAHARA, Y. MORITOMO and Y. TOKURA, *Phys. Rev. B*, **53** (1996) R1689
- [20] P. SVEDLINDH, P. GRANBERG, P. NORDBLAD, L. LUNDGREN, H. S. CHEN, *Phys. Rev. B*, **35** (1987) 268
- [21] K. JONASON, P. NORDBLAD, *J. Magn. Magn. Mater.*, **177-181** (1998) 95
- [22] R. D. SHANNON, *Acta Cryst.*, **A 32** (1976) 751

TABLE I – Structural data for all compositions: average A-site ionic radius $\langle r_A \rangle$ ($\text{\AA}$), average bond length $Mn - O$ ($\text{\AA}$), bond angle $Mn - O - Mn$ (degrees), and Curie temperature T_c (K); $\langle r_A \rangle$ is calculated using data from [22].

y	Struct.	$\langle r_A \rangle$	$\langle d_{Mn-O} \rangle$	$\theta_{Mn-O-Mn}$	T_c
0	R-3C	1.229	2.080	160.73	252
0.1	(R-3C,Pnma)	1.224	(1.970,1.973)	(159.75,160.11)	240
0.2	Pnma	1.218	1.977	158.23	182
0.3	Pnma	1.213	1.976	157.98	165
0.4	Pnma	1.208	1.972	157.97	167

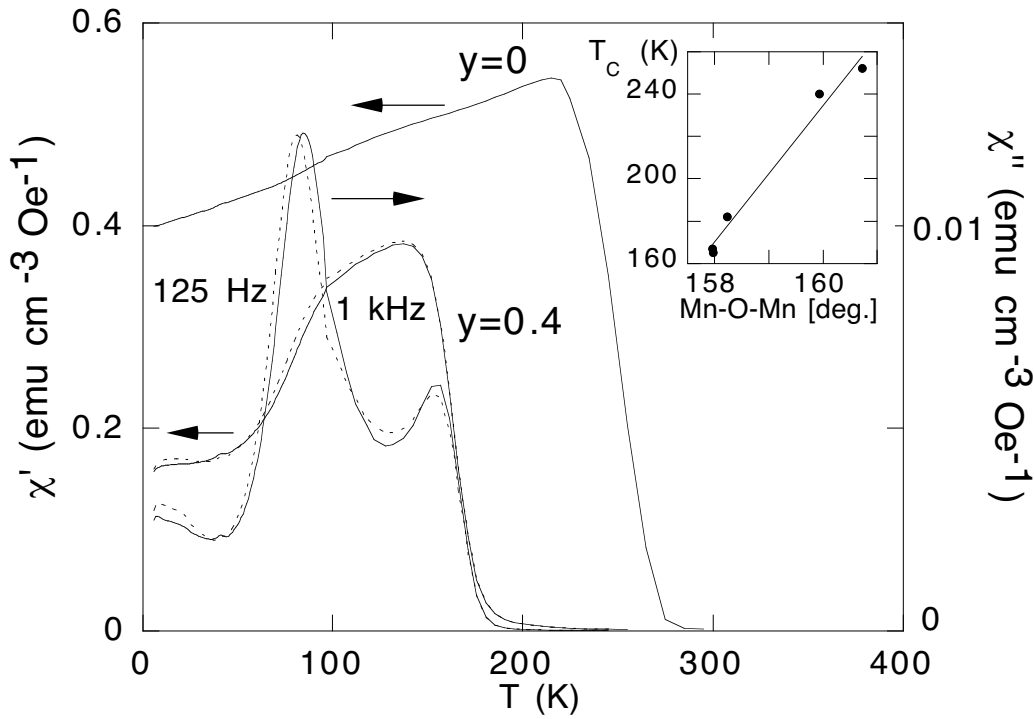


Fig. 1 – In-phase component of the ac-susceptibility for $y=0$ and $y=0.4$. For $y=0.4$, the out-of-phase component is added, and two frequencies are presented ($f=125$ Hz and 1000 Hz in dotted lines). The insert shows the variation of T_c with the $Mn - O - Mn$ bond angle.

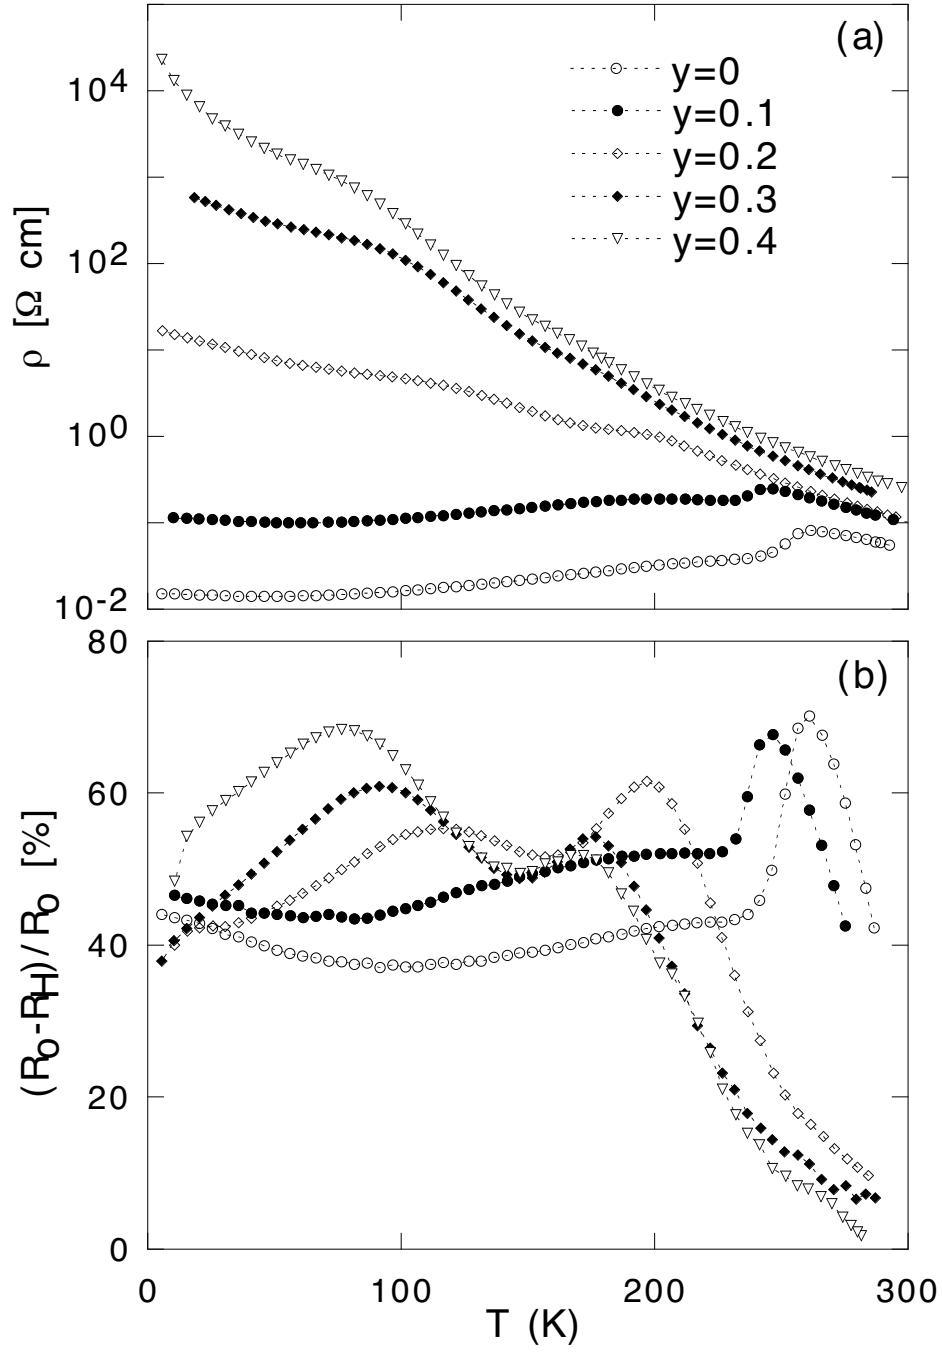


Fig. 2 – Temperature dependence of (a) zero magnetic field resistivity (log. scale) and (b) magnetoresistance for $H=5 \times 10^4$ Oe; the magnetic field is perpendicular to current.

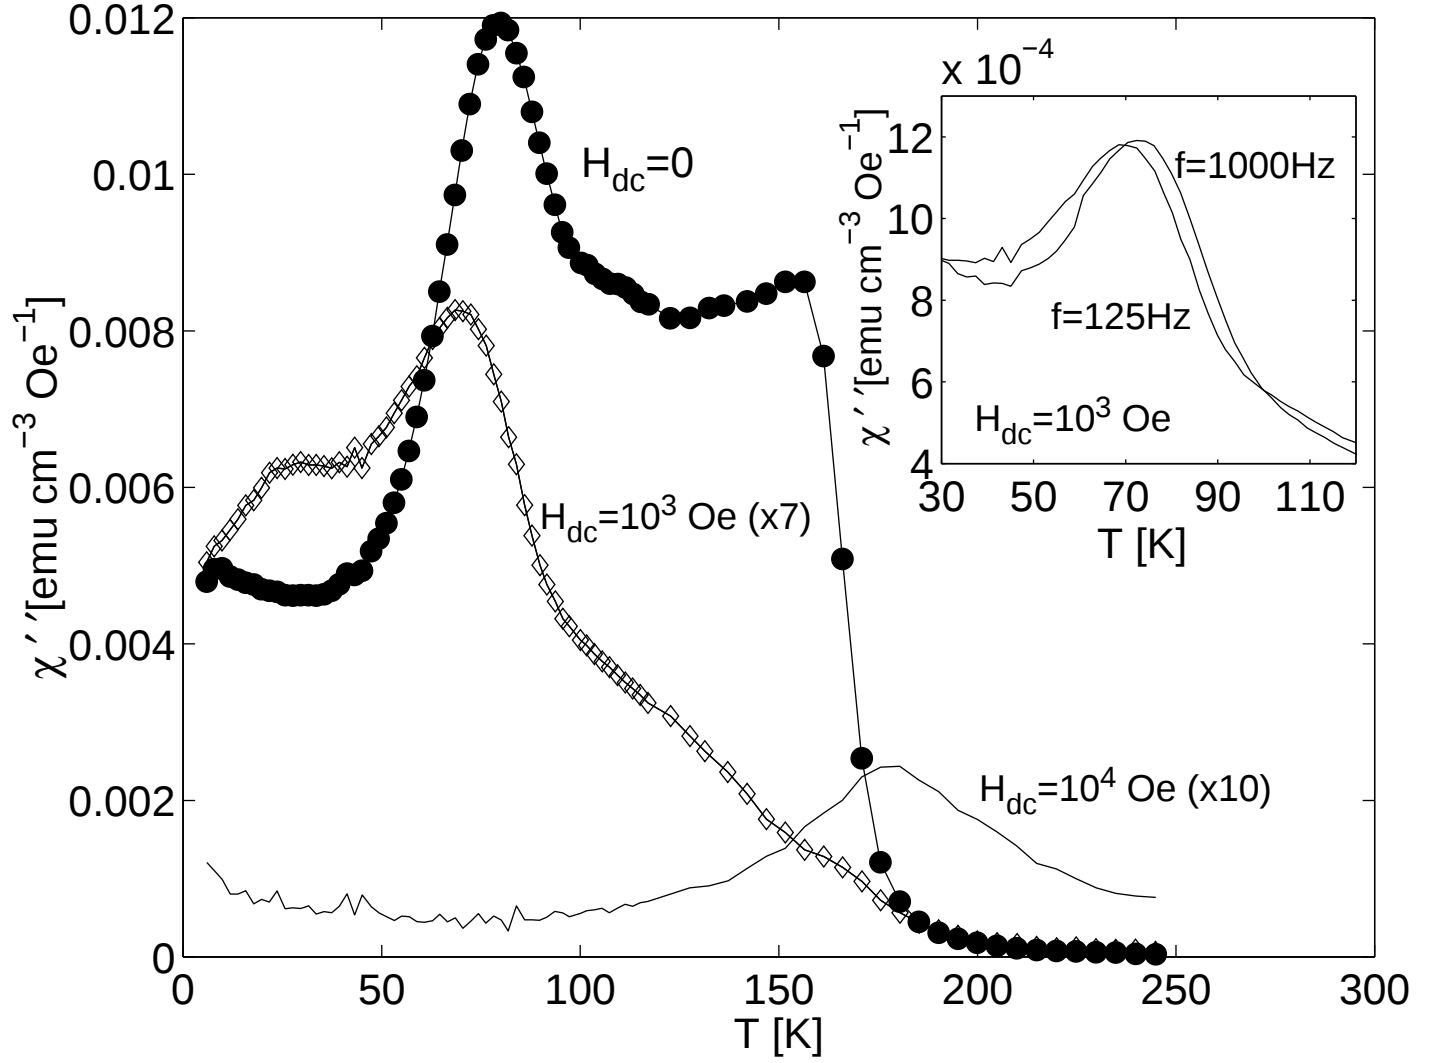


Fig. 3 – Out-of-phase component of the ac-susceptibility for $y=0.4$. $H_{ac}=1$ Oe, and $f=125$ Hz. A dc field H_{dc} is superimposed. The inset shows the frequency dependence of the low temperature peak for $H_{ac}=1$ Oe and $H_{dc}=1000$ Oe.

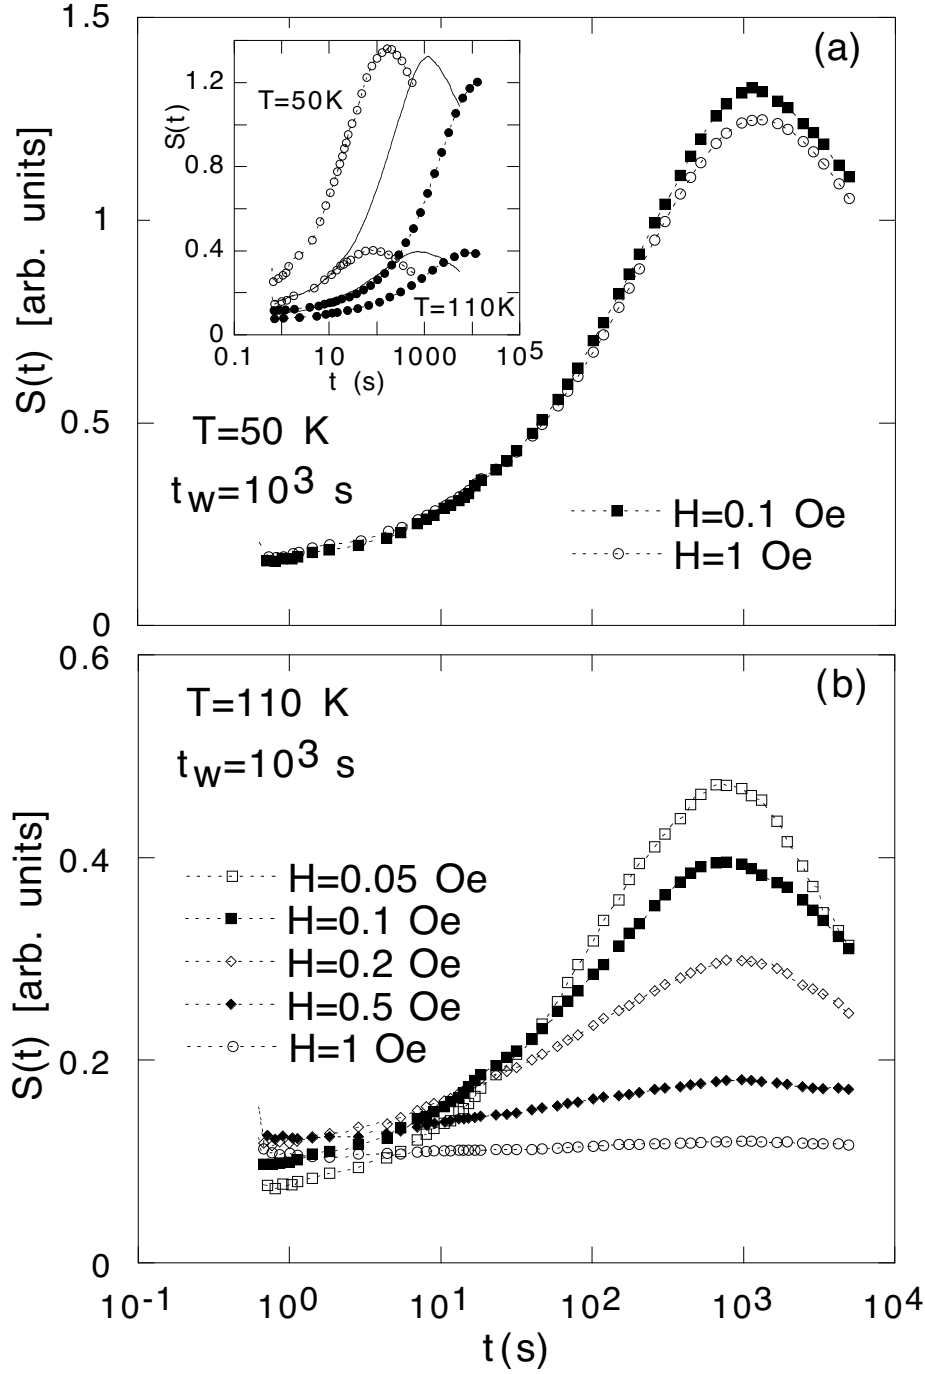


Fig. 4 – Relaxation rate $S(t)$ at $T = 50 \text{ K}$ (a) and $T = 110 \text{ K}$ (b) for different applied probing fields; $t_w = 1000 \text{ s}$. The insert shows the waiting time dependence of $S(t)$ for both temperatures; three different waiting times are used: $t_w = 100 \text{ s}$ (open circles), 1000 s (line) and 10000 s (filled circles); $H_{dc} = 0.1 \text{ Oe}$.